


**Boral Construction Materials
Materials Technical Services**

 Unit 4, 3-5 Gibbon Road
 Baulkham Hills NSW 2153 Australia
 PO Box 400, Winston Hills NSW 2153

T: +61 (02) 9624 9900

F: +61 (02) 9624 9999

www.boral.com.au

TEST REPORT – CURING COMPOUND
Req No: 79927**File No: 130/18****Laboratory Sample No: 208927****Job description:** CURING COMPOUND EVALUATION**Test Method:** AS 3799 - 1998**CLIENT: CHEMCOLOUR INDUSTRIES AUSTRALIA PTY LTD****Address:** 19-25 Anne Street, St. Marys, NSW 2760**Distributor: PARCHEM CONSTRUCTION PRODUCTS****Sample Identification:** Concure WB30 White**Sample Description:** Wax emulsion curing compound**Classification:** Class A, Type 2**Source of sample:** supplied by client: Chemcolour**Date of sampling:** submitted by client: 03/08/2018**Date of test: 21/9-04/10/2018****Method of application:** by spraying at standard application rate of 5m²/L**TEST RESULTS:**

Standard property, Test (Method)	Specification	Result
Water retention efficiency AS 3799.3.1.2 (Method AS 3799 Appendix B)	Min. 90 %	90%
Non - volatile content AS 3799.3.1.8 (Method AS 1580.301.1/ RTA T865)	N / A	34.2%
Density AS 3799.3.1.9 (Method AS 1580.202.2)	N / A	0.982
Viscosity AS 3799.3.1.5 (Method AS 1580.214.5)	Min. 0.05 Pa's	1.27 Pa's
Drying Time AS 3799.3.1.4 (Method AS 1160 Appendix C)	Max. 4 hrs	3 hrs
Infrared absorption spectrum AS 3799.3.2 (Boral Method)	N / A	attached
Stability of emulsion T 862 (RTA 3203)	Max 4 %	2.1%
Residue 150µm AS 3799.3.1.6 (Method AS/NZS 2341.20)	Max. 0.2%	0.08%

 NATA accreditation does not cover
 performance of these tests

The sample submitted and identified by the client.

Juliana Manalang, Mat File, File



Approved Signatory

Julius Alvaro

Date

05/10/18


Serial No.

17 2 5 3 3

Accredited for compliance with ISO/IEC 17025

NATA Accredited Laboratory

Number: 547

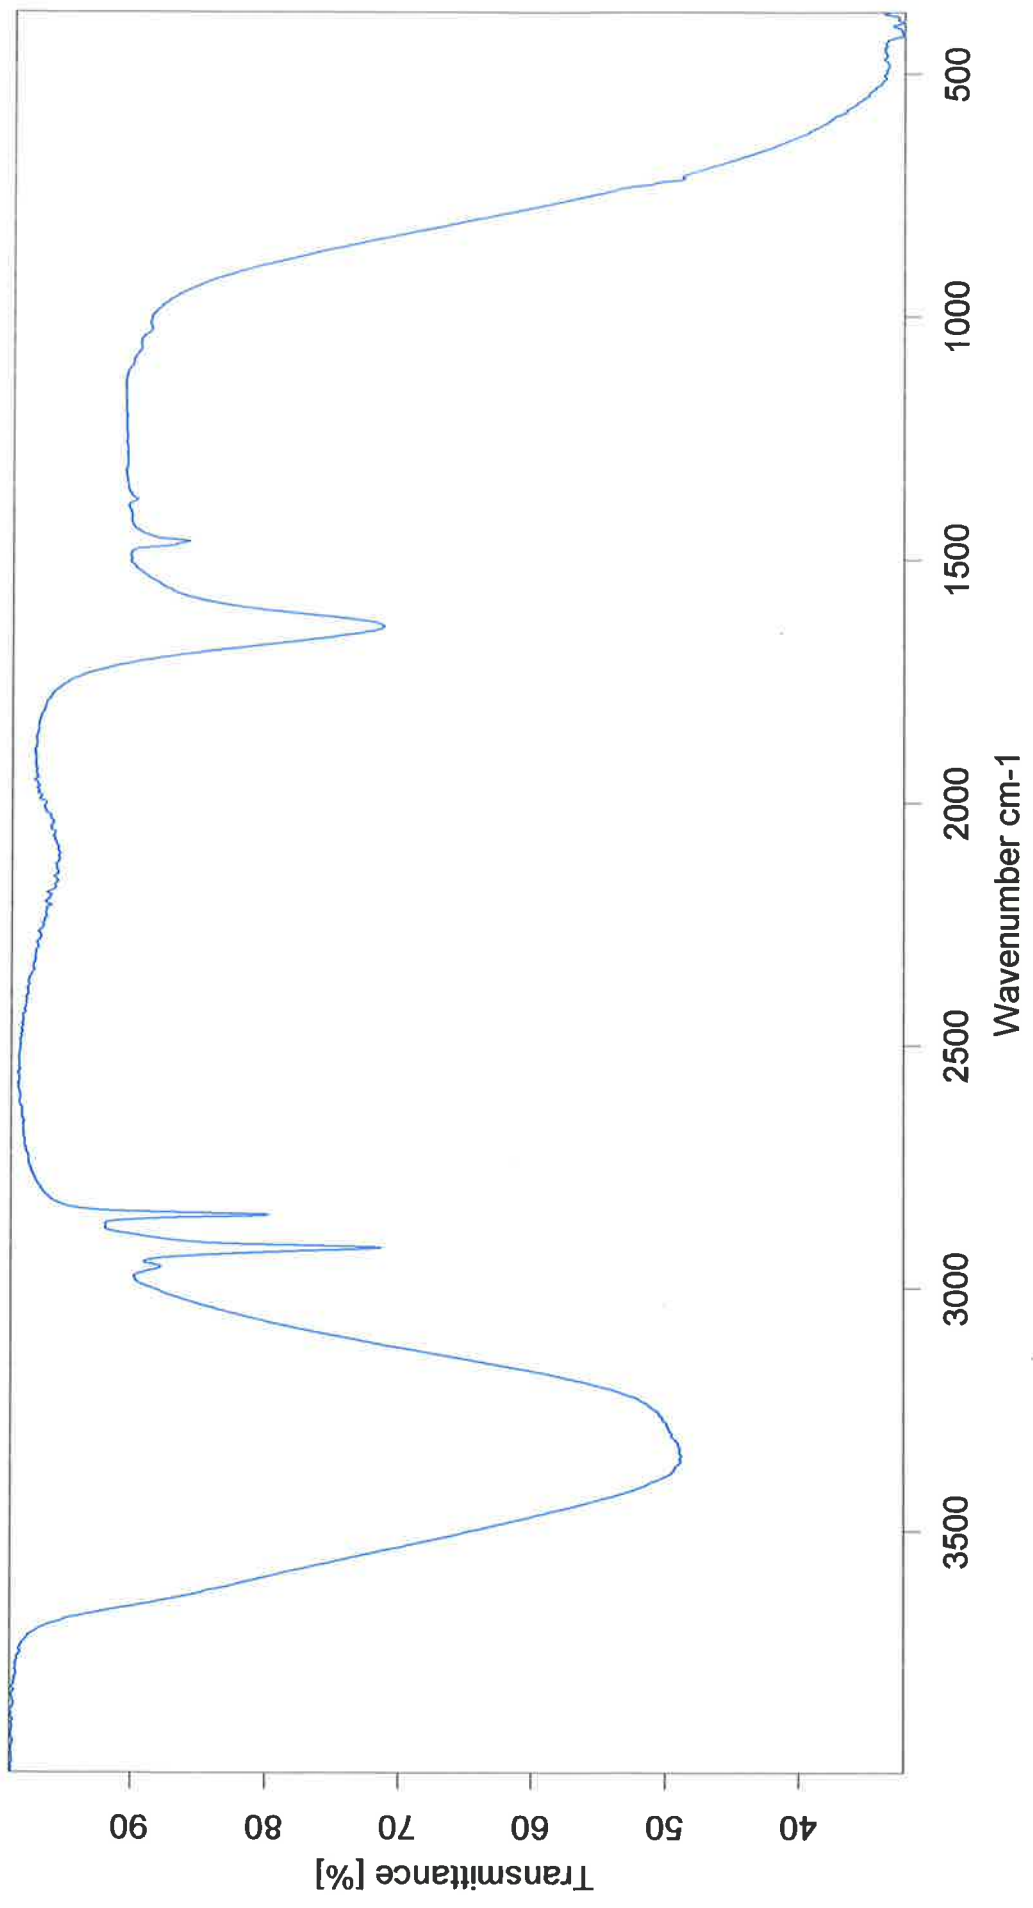

LSN 208927 Distributor : Parchem Construction Products Product : Concure WB White NO 08 / 10/18